

The Dichotomy between Nodal and Antinodal Quasiparticles in Underdoped $(\text{La}_{2-x}\text{Sr}_x)\text{CuO}_4$ Superconductors

X. J. Zhou^{1,2}, T. Yoshida^{1,3}, D.-H. Lee^{4,5}, W. L. Yang^{2,1}, V. Brouet^{1,2}, F. Zhou⁶, W. X. Ti⁶, J. W. Xiong⁶, Z. X. Zhao⁶, T. Sasagawa¹, T. Kakeshita⁷, H. Eisaki⁷, S. Uchida⁷, A. Fujimori³, Z. Hussain² and Z.-X. Shen¹¹

1

¹*Dept. of Physics, Applied Physics and Stanford Synchrotron Radiation Laboratory, Stanford University, Stanford, CA 94305*

²*Advanced Light Source, Lawrence Berkeley National Lab, Berkeley, CA 94720*

³*Dept. of Physics, University of Tokyo, Bunkyo-ku, Tokyo 113, Japan*

⁴*Dept. of Physics, University of California at Berkeley, Berkeley, CA 94720.*

⁵*Material Science Division, Lawrence Berkeley National Lab, Berkeley, CA 94720*

⁶*National Lab for Superconductivity, Institute of Physics, Chinese Academy of Sciences, Beijing 100080, China*

⁷*Dept. of Superconductivity, University of Tokyo, Bunkyo-ku, Tokyo 113, Japan*

(Dated: June 26, 2003)

High resolution angle-resolved photoemission measurements on underdoped $(\text{La}_{2-x}\text{Sr}_x)\text{CuO}_4$ system show that, at energies below 70 meV, the quasiparticle peak is well defined around the $(\pi/2, \pi/2)$ nodal region and disappears rather abruptly when the momentum is changed from the nodal point to the $(\pi, 0)$ antinodal point along the underlying “Fermi surface”. It indicates that there is an extra low energy scattering mechanism acting upon the antinodal quasiparticles. We propose that this mechanism is the scattering of quasiparticles across the nearly parallel segments of the Fermi surface near the antinodes.

PACS numbers: 74.25.Jb, 71.18.+y, 74.72.Dn, 79.60.-i

The high temperature superconductivity in cuprates is derived from doping the parent antiferromagnetic Mott insulators. It is found that the normal state properties of cuprates are highly anomalous, particularly in the underdoped region. Understanding the normal state is believed to be a key for understanding the mechanism of high temperature superconductivity[1].

For the underdoped cuprates, one peculiar behavior of its electronic structure, as revealed by angle-resolved photoemission spectroscopy (ARPES), is the dichotomy between the $\sim (\pi/2, \pi/2)$ nodal and $\sim (\pi, 0)$ antinodal excitations. In underdoped $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$ (Bi2212), it was found that the lineshape of the *normal state* photoemission spectra is broad in the antinodal region but sharp near the nodal region[2]. It was proposed that the antinodal spectral broadening in the normal state is due to the coupling of electrons with the (π, π) magnetic excitations[2]. In the superconducting state, the antinodal spectrum is also believed to be influenced by the (π, π) spin resonance mode[3].

The peculiar electronic structure of the underdoped sample may provide important clues for understanding the anomalous normal state properties. It is therefore essential to establish whether such a nodal-antinodal dichotomy is universal in cuprate materials, and particularly, to establish its physical origin. However, Bi2212 is not an ideal system for such an in-depth investigation. Because of disorder, no sharp nodal structure has been observed in deeply underdoped Bi2212. Furthermore, the states near the antinodal region are severely complicated by its superstructure. This, together with the bilayer splitting resolved very recently[4], raises concerns about

the interpretations[5, 6, 7]. The $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ (LSCO) system, in comparison, is an ideal candidate to address the issue in the underdoped region because the system becomes less disordered with decreasing doping. As we will show, one can see an essentially resolution-limited sharp nodal peak in LSCO with a doping level as low as 6.3% which has not been observed in Bi2212 with a comparable doping. Its simple crystal structure also makes it free from the complications of the superstructure and bilayer splitting encountered in Bi2212.

While the majority of photoemission work so far has been performed on Bi2212, data on LSCO are available only recently because of the improved sample quality and better understanding of matrix element effects involved in measuring LSCO system[8, 9, 10]. In this paper, we present detailed angle-resolved photoemission data on underdoped LSCO superconductors. We observe remarkably sharp nodal quasiparticle peak at all doping levels studied, even for heavily underdoped samples. In contrast, the antinodal peak only exists in optimally-doped and overdoped samples. Particularly, these sharp peaks can be observed only at low energy, below 70 meV. In addition, for underdoped samples, when moving from nodal to antinodal regions, we find that the disappearance of sharp peaks occurs in a fairly abrupt fashion near where the Fermi surface changes from parallel to the $(\pi, 0)$ - $(0, \pi)$ diagonal to parallel to the $(0, 0)$ - $(\pi, 0)$ or $(0, 0)$ - $(0, \pi)$ directions. Intrigued by the close tie between the quasiparticle scattering and the Fermi surface topology, we propose this “nodal-antinodal dichotomy” is due to the scattering of quasiparticles across the almost parallel segments of the Fermi surface near the antinodes.

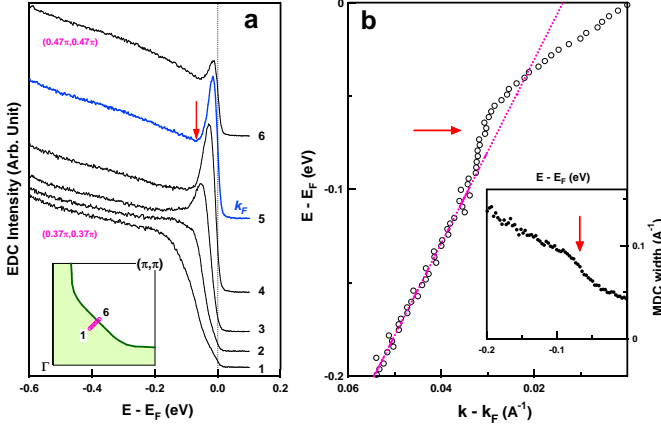


FIG. 1: Electronic structure of LSCO ($x=0.063$, $T_c=12$ K) along the $(0,0)$ - (π,π) nodal direction (inset of Fig. 1a) at a temperature of 20 K. (a). EDCs measured along the nodal direction in a second Brillouin zone. The EDCs are numbered according to the momentum points in the inset. These momentum points are equal spaced: point 1 corresponds to $(0.374\pi, 0.374\pi)$ and point 6 corresponds to $(0.466\pi, 0.466\pi)$. The red arrow indicates an energy of ~ 70 meV below which the quasiparticle survives and above which it turns into a broad edge. (b). A kink in the dispersion at ~ 70 meV as indicated by an arrow. The dotted pink line is a guide to the eye which is a line fitting the high-energy part of the dispersion. In the inset is the MDC width which shows a drop at an energy of ~ 70 meV, as indicated by an arrow.

The photoemission measurements were carried out on beamline 10.0.1 at Advanced Light Source, using a Scienta 2002 electron energy analyzer. The photon energy is 55 eV and the \vec{E} -vector of the incident light is parallel to the CuO_2 plane and 45° with respect to the Cu-O bond, as indicated by the arrow in Fig. 2a[8, 9]. The energy resolution is 15–20 meV and the angular resolution is 0.3° (corresponding to 0.018 \AA^{-1} in momentum). In this paper we mainly present our data on the underdoped LSCO ($x=0.063$, $T_c=12$ K) and LSCO ($x=0.09$, $T_c=28$ K) samples. For comparison, we also show data on overdoped LSCO ($x=0.22$, $T_c=24$ K). The LSCO single crystals are grown by travelling solvent floating zone method[11]. The samples were cleaved *in situ* in vacuum with a base pressure better than 4×10^{-11} Torr and measured at a temperature of ~ 20 K.

Fig. 1 presents experimental results along the $(0,0)$ - (π,π) nodal direction of the LSCO ($x=0.063$) sample. Even for this extremely underdoped sample in the vicinity of an insulator-superconductor transition, one can see a remarkably sharp quasiparticle peak in the nodal region with a clear dispersion (Fig. 1a). The sharp peak abruptly turns into an edge once it disperses up to an energy of ~ 70 meV. Such a dramatic change in spectral shape is not observed in underdoped Bi2212, presumably due to stronger disorder in Bi2212. The dispersion (Fig.

1b), extracted by fitting momentum distribution curves (MDCs)[10, 12, 13, 14, 15], shows a clear slope break (a kink) at an energy ~ 70 meV. The MDC width, which is related to the scattering rate τ^{-1} , also exhibits a drop at the same energy (inset of Fig. 1b). All these observations indicate that there is an energy scale at ~ 70 meV for the nodal quasiparticles.

Fig. 2a shows the low-energy spectral weight of the LSCO ($x=0.063$) sample as a function of momentum by integrating EDCs in a narrow energy window near E_F (-5 meV, 5 meV) (k_x and k_y are along Cu-O bonding direction). The high intensity contour constitutes what we call the “Fermi surface”[16]. To be quantitative, we used MDCs at E_F to extract the Fermi momentum (k_F) by following the MDC peak position. This is exemplified in the inset of Fig. 2a for nine cuts in a second zone and the obtained k_F s are marked as red crosses in Fig. 2a. The k_F s are obtained in another second zone and the first zone in a similar manner although the relative spectral intensity in the first Brillouin zone is much weaker. Covering multiple Brillouin zones allows us to align the sample to high precision because it provides an internal check: the Fermi surfaces obtained from different zones have to be consistent with each other. The final extracted Fermi surface is plotted in Fig. 3. To a good approximation, the measured Fermi surface can be represented as three straight segments: two antinodal ones (marked black in Fig. 3) running parallel to $(0,0)$ - $(\pi,0)$ and $(0,0)$ - $(0,\pi)$ directions, respectively, and the nodal one (marked red in Fig. 3) running parallel to $(\pi,0)$ - $(0,\pi)$ diagonal direction.

Fig. 2(b1-b9) shows the energy distribution curves (EDCs) along nine cuts of the Fermi surface from the nodal to the antinodal region (as marked in Fig. 2a) for the $x=0.063$ sample. The red curves are the EDCs at $k = k_F$. It is clear that all quasiparticle peaks are confined within 70 meV energy range near the Fermi level. Moreover, the quasiparticle peaks exist only on part of the Fermi surface near the nodes, as marked by the solid red line in Fig. 3. Away from the “nodal segment” the peak gets weaker and disappears in a fairly abrupt fashion. This can be seen more clearly from Fig. 4a where the EDCs on the underlying Fermi surface and at $(\pi,0)$ are plotted together. Similar sharp transition is also observed in another underdoped LSCO ($x=0.09$) sample (Fig. 4b). The situation for these underdoped samples is very different from that in the highly overdoped ($x=0.22$) sample (Fig. 4c). In that case we see quasiparticle peak over the entire Fermi surface; the antinodal peak appears even sharper than the nodal peak. This doping dependence clearly indicates that the spectral broadening near the antinodal region in the underdoped samples is *not due to a matrix element effect*. This is also consistent with earlier observations in Bi2212[2].

At first glance, the concept of quasiparticle seems entirely inappropriate for heavily underdoped cuprates.

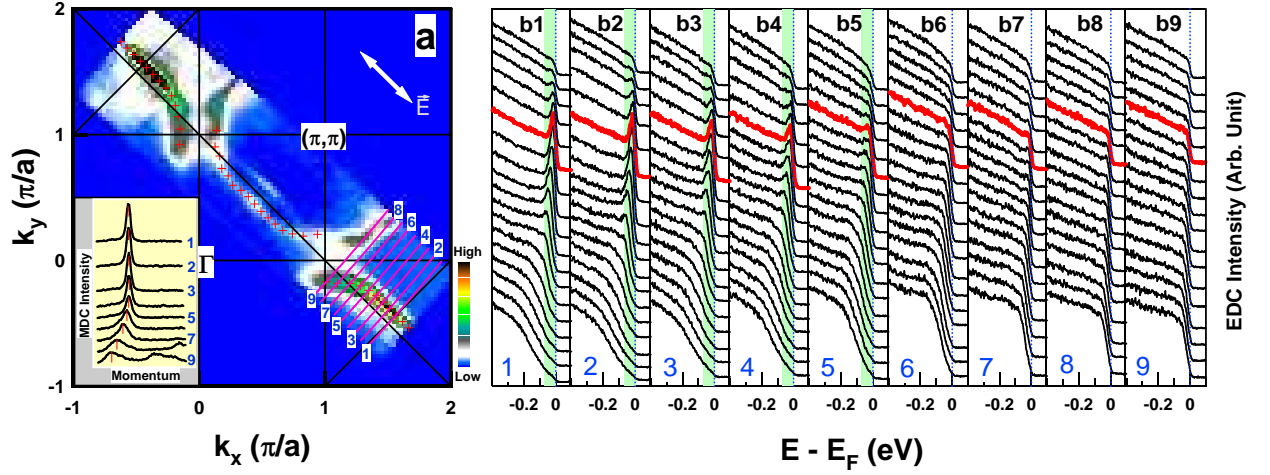


FIG. 2: (a). Low energy spectral weight as a function of k_x and k_y for the LSCO $x=0.063$ sample measured at a temperature of 20 K. The inset shows MDCs at E_F along several momentum cuts in one octant of the second Brillouin zone; the corresponding cuts are marked in the figure with a number from 1 to 9. The red cross in the figure represents the peak position of MDCs at E_F . (b1-b9). EDCs along the cuts as marked in (a). The red spectra are EDCs on the underlying Fermi surface. The green shades in (b1-b5) highlight the energy range (0~70 meV) within which sharp peaks are confined.

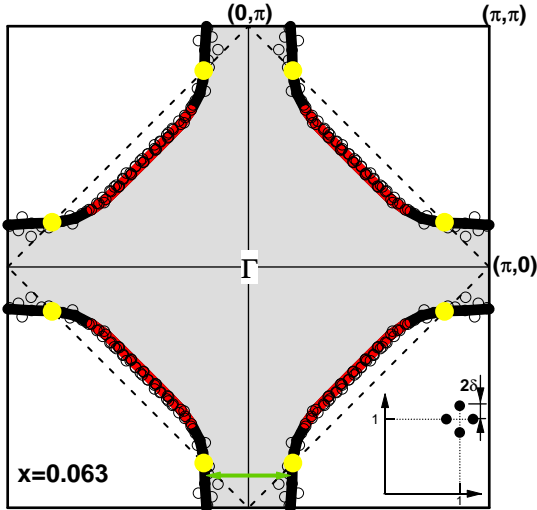


FIG. 3: Experimental Fermi surface for LSCO $x=0.063$ sample. The black open circles are obtained from the MDC peak position at E_F , as shown in Fig. 1 as the red crosses, and then symmetrized in the first Brillouin zone. The solid lines are guides to the eye for the measured Fermi surface. The red lines represent the portion of Fermi surface where one can see quasiparticle peaks. The dotted black line represents the antiferromagnetic Brillouin zone boundary; its intersection with the Fermi surface gives eight "hot spots" (solid yellow circles) from (π, π) magnetic excitations. The double-headed green line represents a nesting vector, $(0.35\pi, 0)$, between the antinodal part of the Fermi surface. In the inset shows the schematic neutron diffraction pattern observed in LSCO superconductors with four incommensurate peaks of distance 2δ from (π, π) point.

Given the fact that we are dealing with a strongly correlated system, the existence of sharp nodal quasiparticle below 70 meV is itself a miracle, not to mention the nodal-antinodal dichotomy. One might argue that the nodal-antinodal dichotomy is due to the much higher excitation energy near the antinodes compared to that near the nodes, as often assumed in the theory literature. We stress that the antinodal edge (~ 15 meV) discussed in this paper is not particularly high in energy compared to that of some nodal peaks (Fig. 4) and is definitely below 70 meV along the Fermi surface locus. Therefore, this trivial explanation does not work. The spirit of our paper is to assume the existence of a mechanism that allows *all* low energy quasiparticles below 70 meV. Under the working of this mechanism both low energy nodal and antinodal excitations become sharp Bogoliubov-Landau quasiparticles. The Fermi surface map should also be taken in this context. Here we put the phrase "Fermi surface" in quotation marks to reflect the fact that by that we mean the locus of the lowest energy quasiparticle excitations before the extra scattering on antinodal excitations is switched on. Then we ask what extra is needed to explain the antinodal spectral broadening.

One candidate that immediately comes to mind is the (π, π) magnetic fluctuation that produces "hot spots" on the Fermi surface, as previously proposed for Bi2212[2]. We note that neutron scattering has revealed a significant difference in the magnetic response of LSCO and Bi2212. The (π, π) spin resonance mode observed in Bi2212[17] is absent in LSCO. Instead, incommensurate magnetic peaks were observed at low energy (below 15 meV)[18, 19, 20] (inset of Fig. 3), which broaden rapidly with increasing energy although the magnetic fluctuation

can persist up to 280 meV[21]. To check whether the low energy incommensurate magnetic fluctuation can be responsible for the lack of spectral peaks in the antinodal segments, we have performed the following analysis. First, we shift the measured Fermi surface by the peak wave vectors of the magnetic excitation $((\pi, \pi) \pm (2\delta, 0)$ and $(\pi, \pi) \pm (0, 2\delta)$ with δ being the incommensurability) to produce four Fermi surface replicas. Then we record the intersections of these replicas with the original Fermi surface. These intersections are “hot spots” where the quasiparticles will experience scattering from the incommensurate magnetic fluctuations. For $x = 0.063$ and $x = 0.09$ samples the obtained hot spots do concentrate around the antinodes. However, for $x = 0.15$ and $x = 0.22$ samples the above construction also leads to “hot spots” mainly near the antinodal segments but the quasiparticle peak can be seen over the entire Fermi surface. Considering that the incommensurate peaks are present in LSCO up to $x=0.25$ [20], this latter observation is inconsistent with the mechanism of the incommensurate magnetic fluctuations although one can not completely rule out this possibility because how the coupling strength varies with doping is not known.

Intrigued by the fact that the extra broadening sets in when the Fermi surface turns from the $(\pi, 0)$ - $(0, \pi)$ diagonal direction to $(0, 0)$ - $(\pi, 0)$ or $(0, 0)$ - $(0, \pi)$ direction, we propose an alternative mechanism that the scattering in question causes a pair of electrons on two parallel antinodal segments to be scattered to the opposite ones (Fig. 3), *i.e.*, $\mathbf{p}_1 = (\pm 0.175\pi, p_{1y})$, $\mathbf{p}_2 = (\mp 0.175\pi, p_{2y}) \rightarrow \mathbf{p}'_1 = (\mp 0.175\pi, p_{1y})$, $\mathbf{p}'_2 = (\pm 0.175\pi, p_{2y})$, or $\mathbf{p}_1 = (p_{1x}, \pm 0.175\pi)$, $\mathbf{p}_2 = (p_{2x}, \mp 0.175\pi) \rightarrow \mathbf{p}'_1 = (p_{1x}, \mp 0.175\pi)$, $\mathbf{p}'_2 = (p_{2x}, \pm 0.175\pi)$. In the normal state this scattering mechanism can cause a quasiparticle to decay into two quasiparticles

and one quasihole. The antinodal spectral broadening occurs as a result of the frequent occurrence of such a decay which renders the normal state quasiparticle ill-defined.

In summary, we have shown that the low energy excitations between nodal and antinodal quasiparticles behave very differently in the underdoped superconductors. Evidently such a dichotomy is due to the existence of an extra *low energy* scattering mechanism that operates primarily on antinodal quasiparticles. We propose this may be associated with quasiparticle scattering across the nearly parallel segments of the Fermi surface near the antinodes. Clearly this proposal requires more scrutiny, both experimentally and theoretically.

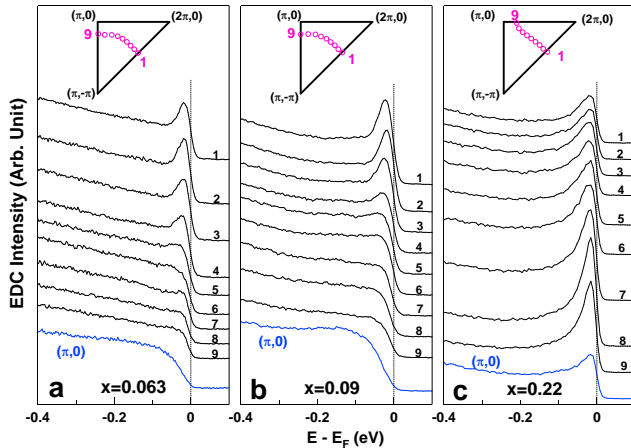


FIG. 4: EDCs on Fermi surface for LSCO $x=0.063$ (a), 0.09 (b) and 0.22 (c) samples. All samples are measured at ~ 20 K. The corresponding momentum position is marked in the upper inset of each panel. Also included are the spectra at $(\pi, 0)$ points, colored as blue.

- [1] P. W. Anderson and R. Schrieffer, *Physics Today* **44**, 54-61 (1991).
- [2] Z.-X. Shen and J. R. Schrieffer, *Phys. Rev. Lett.* **78**, 1771(1997).
- [3] J. C. Campuzano et al., *Phys. Rev. Lett.* **83**, 3709 (1999).
- [4] D. L. Feng et al., *Phys. Rev. Lett.* **86**, 5550 (2001); Y. D. Chuang et al., *Phys. Rev. Lett.* **87**, 117002 (2001); P. V. Bogdanov et al., *Phys. Rev. B* **64**, 180505R (2001).
- [5] T. K. Kim et al., *Phys. Rev. Lett.* **91**, 167002 (2003).
- [6] M. Eschrig and M. R. Norman, *Phys. Rev. Lett.* **89**, 277005 (2002).
- [7] A. D. Gromko et al., *condmat/0202329*.
- [8] X. J. Zhou, et al., *Phys. Rev. Lett.* **86**, 5578 (2001).
- [9] T. Yoshida et al., *Phys. Rev. B* **63**, (2001) 220501.
- [10] X. J. Zhou et al., *Nature (London)* **423**, 398 (2003).
- [11] F. Zhou et al., *Supercon. Sci. Technol.* **16**, L7 (2003).
- [12] P. V. Bogdanov et al., *Phys. Rev. Lett.* **85**, 2581 (2000).
- [13] A. Kaminski et al., *Phys. Rev. Lett.* **86**, 1070 (2001).
- [14] A. Lanzara et al., *Nature (London)* **412**, 510(2001).
- [15] P. D. Johnson et al., *Phys. Rev. Lett.* **87**, 177007 (2001).
- [16] Throughout the paper we use the phrase “Fermi surface” loosely to denote the momentum space locus of high intensity low-energy spectral weight.
- [17] H. F. Fong et al., *Nature (London)* **398**, 588 (1999).
- [18] J. M. Tranquada et al., *Nature* **375**, 561 (1995).
- [19] G. Aeppli et al., *Science* **278**, 1432 (1997).
- [20] K. Yamada et al., *Phys. Rev. B* **57**, 6165 (1998).
- [21] S. M. Hayden et al., *Phys. Rev. Lett.* **76**, 1344 (1996).
- [22] The experiment was performed at the ALS of LBNL, which is operated by the DOE’s Office of BES, Division of Material Science, with contract DE-FG03-01ER45929-A001. The division also provided support for the work at SSRL with contract DE-FG03-01ER45929-A001. The work at Stanford was also supported by NSF grant DMR-0304981 and ONR grant N00014-98-1-0195-P0007. The work in Japan is supported by a Grant-in-Aid for Scientific Research in the Priority Area “Novel Quantum Phenomena in Transition-Metal Oxides” from the Ministry of Education, Culture, Sports, Science and Technology of Japan and the New Energy and Industrial Technology Development Organisation (NEDO). The work in China is supported by National Natural Science Foundation of China and Ministry of Science and Technology of China through Project 10174090 and Project G1999064601.